SANDVIK

# SANDVIK 2RK65™
# TUBE AND PIPE, SEAMLESS

DATASHEET

Sandvik 2RK65™ is a high-alloy austenitic stainless steel intended for use under severe corrosive conditions within the process industry. The grade is characterized by:

- Very good resistance to attacks in acidic environments, e.g. sulfuric, phosphoric and acetic acid
- Very good resistance to pitting in neutral chloride-bearing solutions
- Much better resistance to crevice corrosion than steels of the ASTM 304 and ASTM 316 types
- Very good resistance to stress corrosion cracking
- Good weldability

## STANDARDS

- ASTM: '904L'
- UNS: N08904
- ISO: 4539-089-04-I
- EN Number: 1.4539
- EN Name: X1NiCrMoCu25-20-5

### Product standards

- ASTM A213 (seamless/welded tube)
- ASTM A269 (seamless/welded tube)
- ASTM A312 (seamless/welded pipe)
- ASTM A240 (plate and sheet)
- ASTM A276, A479, A484 (bar)
- ASTM B677 (seamless tube and pipe)
- EN 10216-5 (seamless tube and pipe)

### Approvals

- Approved for use in ASME Boiler and Pressure Vessel Code section VIII, div. 1 construction
- VdTÜV-Werkstoffblatt 421 (Austenitischer Walz-und Schmiedestahl)

## CHEMICAL COMPOSITION (NOMINAL)

**Chemical composition (nominal) %**

| C | Si | Mn | P | S | Cr | Ni | Mo | Cu |
|---|---|---|---|---|---|---|---|---|
| ≤0.020 | 0.5 | 1.8 | ≤0.025 | ≤0.015 | 20 | 25 | 4.5 | 1.5 |

## APPLICATIONS

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

Typical applications for Sandvik 2RK65™ are found in oil refineries and within the chemical and petrochemical industry. Sandvik 2RK65™ is also used within the pulp and paper industry, the mineral and metallurgical industry, the food industry, in seawater cooling and in many other fields.

The grade is an excellent alternative to standard austenitic stainless steels in heat exchangers using high-temperature water with chloride contamination.

## CORROSION RESISTANCE

### General corrosion

The steel was originally developed for use in **sulfuric acid**. Its good resistance is achieved by virtue of a high molybdenum content and alloying with copper. Figure 1 is an isocorrosion diagram for Sandvik 2RK65™, Sanicro® 28 and ASTM 316L in deaerated sulfuric acid.

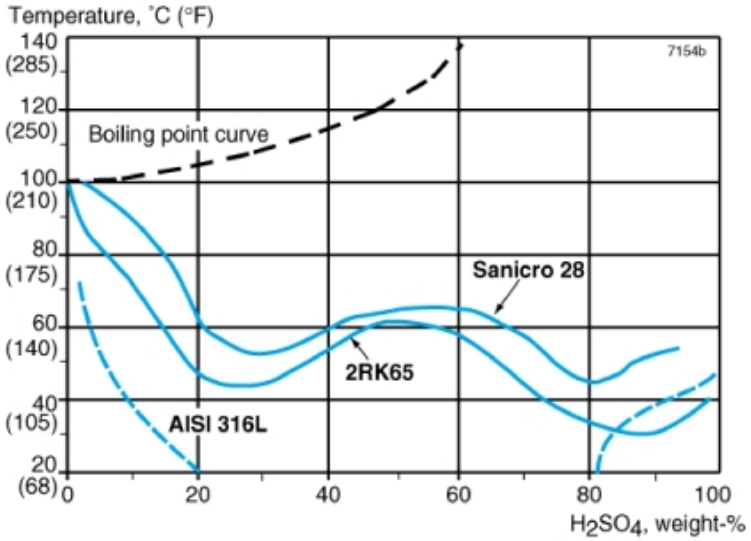



Figure 1. Isocorrosion diagram for Sandvik 2RK65, Sanicro 28 and ASTM 316L in deaerated sulfuric acid at a corrosion rate of 0.1 mm/year (4 mpy) in stagnant solution.

Figure 2 shows the isocorrosion diagram for the above steels but in naturally aerated sulfuric acid.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

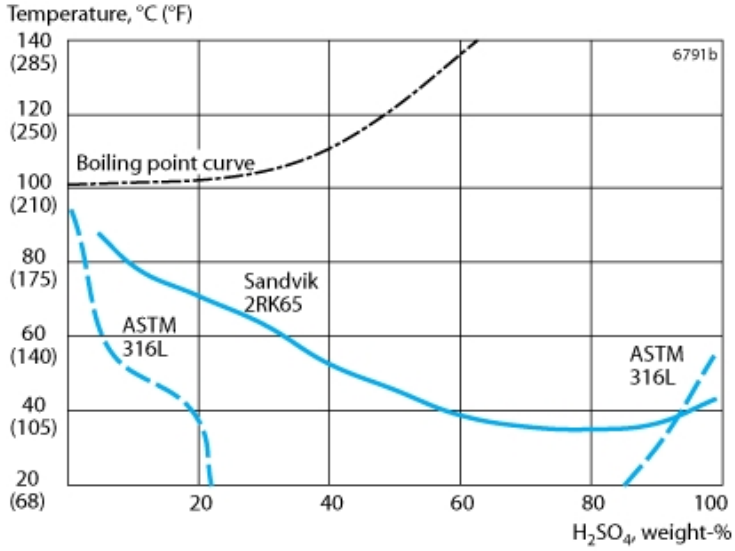



Figure 2. Isocorrosion diagram 0.1 mm/year (4 mpy) for Sandvik 2RK65 and ASTM 316L in naturally aerated sulfuric acid of chemical purity.

Technical **phosphoric acid** manufactured by means of the 'wet' method contains varying amounts of impurities from the starting material, the phosphate rock. The most dangerous of these impurities are chlorides, $Cl^-$, and fluorides in free form, $F^-$. Sandvik 2RK65 has been used with success in many applications in phosphoric acid plants and for the handling of technical acid. However, for the severest corrosion conditions, Sanicro® 28, which was developed especially for phosphoric acid applications, provides superior corrosion resistance.

In pure **acetic acid,** both Sandvik 2RK65™ and ASTM 316L are completely resistant at all temperatures and concentrations at atmospheric pressure. At elevated temperatures and pressures, however, ASTM 316L will corrode while Sandvik 2RK65™ will remain resistant. Experience from acetic acid production has shown that acetic acid contaminated with formic acid is always corrosive. In acid of this kind, Sandvik 2RK65 is far more resistant than ASTM 316L, see table 1 below. Practical operating experience has confirmed the superiority of Sandvik 2RK65™ to ASTM 317L as well.

In **formic acid,** high-alloy Sandvik 2RK65™ shows better resistance than conventional steels of the ASTM 316L type, see Figure 3. In **oxalic acid** Sandvik 2RK65™ shows better performance than ASTM 316L, see Figure 4. 2RK65 is resistant (corrosion rate <0.1 mm/year) in **lactic acid** at all concentrations at temperatures up to or slightly below the boiling point at atmospheric pressure. This means a corrosion resistance similar to or slightly better than of ASTM 316L in lactic acid. Due to its molybdenum content, Sandvik 2RK65™ is less resistant to **nitric acid** than steels of the ASTM 304L and ASTM 310L types, which are commonly used in these environments.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

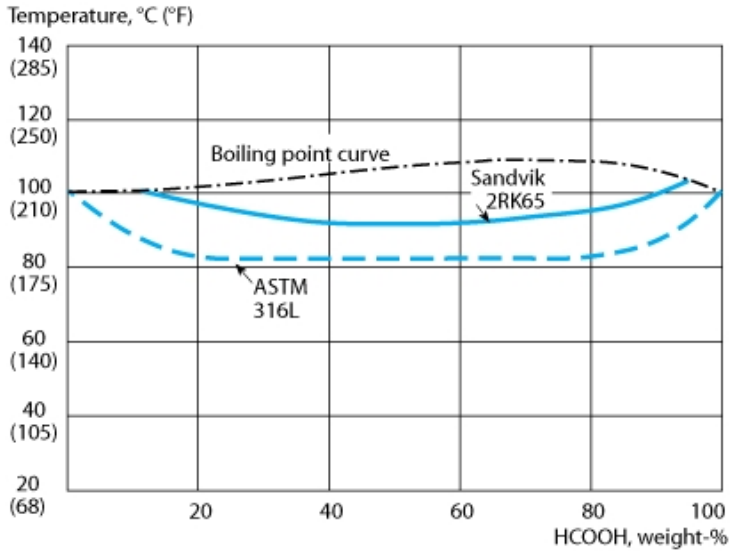



Figure 3. Isocorrosion diagram 0.1 mm/year (4mpy) ior 2RK65 and ASTM 316L in formic acid.

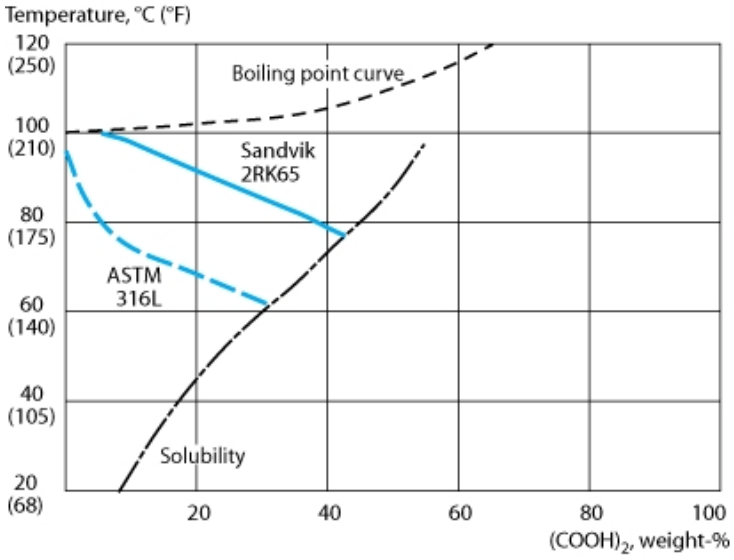



Figure 4. Isocorrosion diagram 0.1 mm/year (4mpy) ior 2RK65 and ASTM 316L in oxalic acid.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

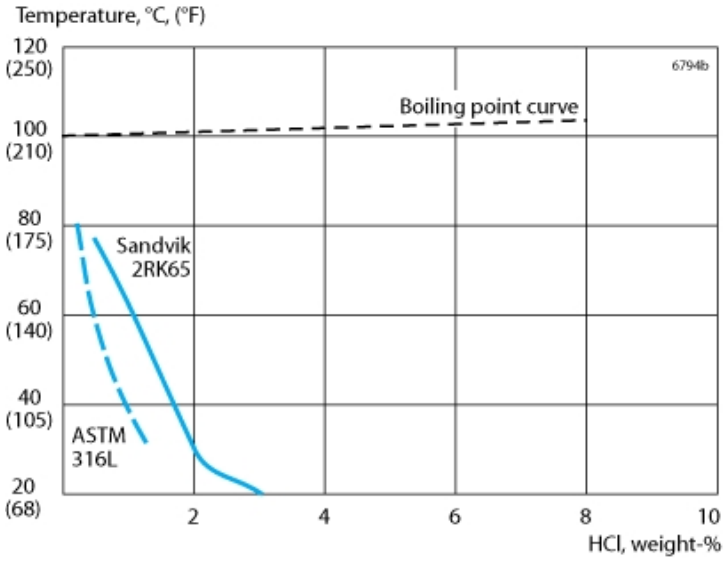



Figure 5. Isocorrosion diagram 0.1 mm/year (4 mpy) ior 2RK65 and AISI 316L in hydrochloric acid.

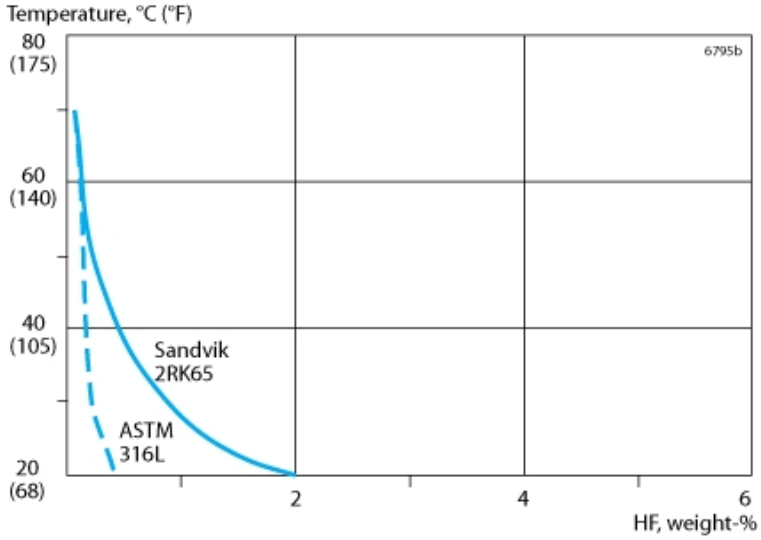



Figure 6. Isocorrosion diagram 0.1 mm/year (4mpy) ior 2RK65 and ASTM 316L in hydrofluoric acid.

High molybdenum content is an advantage in **hydrochloric acid,** and Sandvik 2RK65™, with its 4.5% Mo is consequently far more resistant than, for example, ASTM 316L. Sandvik 2RK65 is therefore suitable for use in chemical process solutions containing small amounts of hydrochloric acid. The isocorrosion diagram is presented in Figure 5. The risk of pitting should, however, be kept in mind. Also in **hydrofluoric acid** Sandvik 2RK65™ benefits from its high molybdenum content, although hydrofluoric acid is an even more aggressive acid compared to hydrochloric acid, see isocorrosion diagram in Figure 6.

Table 1. results of laboratory tests lasting 1+3+3 days in boiling mixtures of acetic and formic acid.

| Acetic acid % | Formic acid % | Corrosion rate | mpy | ASTM 316L | mpy |
|---|---|---|---|---|---|
| | | Sandvik 2RK65 | | | |

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

| | | mm/year | | mm/year | |
|---|---|---|---|---|---|
| 10 | 10 | 0.09 | 3.6 | 0.35 | 14 |
| 25 | 10 | 0.07 | 2.8 | 0.33 | 13 |
| 30 | 10 | 0.10 | 4.0 | 0.29 | 12 |
| 50 | 10 | 0.10 | 4.0 | 0.27 | 11 |

Due to its high chromium and nickel contents, Sandvik 2RK65™ possesses much better resistance in **sodium hydroxide** than ASTM 304 and ASTM 316, see Figure 7.

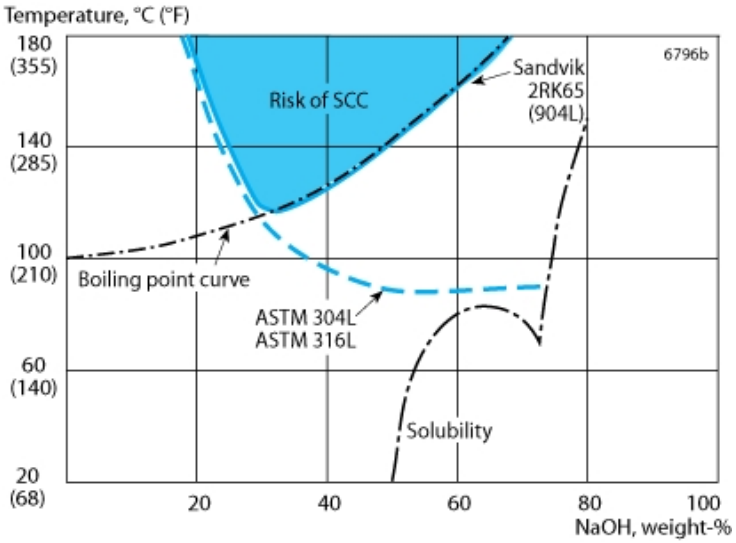



Figure 7. Isocorrosion diagram 0.1 mm/year (4mpy) ior 2RK65, 304L and AISI 316L in sodium hydroxide of chemical purity.

As can be seen, the risk of stress corrosion cracking (SCC) increases at high temperatures. This risk is enhanced if chlorides are present. The alloy Sanicro® 28 provides better resistance against stress corrosion cracking and also general corrosion than is the case for Sandvik 2RK65™.

### Pitting corrosion

The high chromium and molybdenum contents of this steel make it very resistant to pitting. This has been verified by extensive practical experience of service involving chloride-bearing process solutions and seawater cooling.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

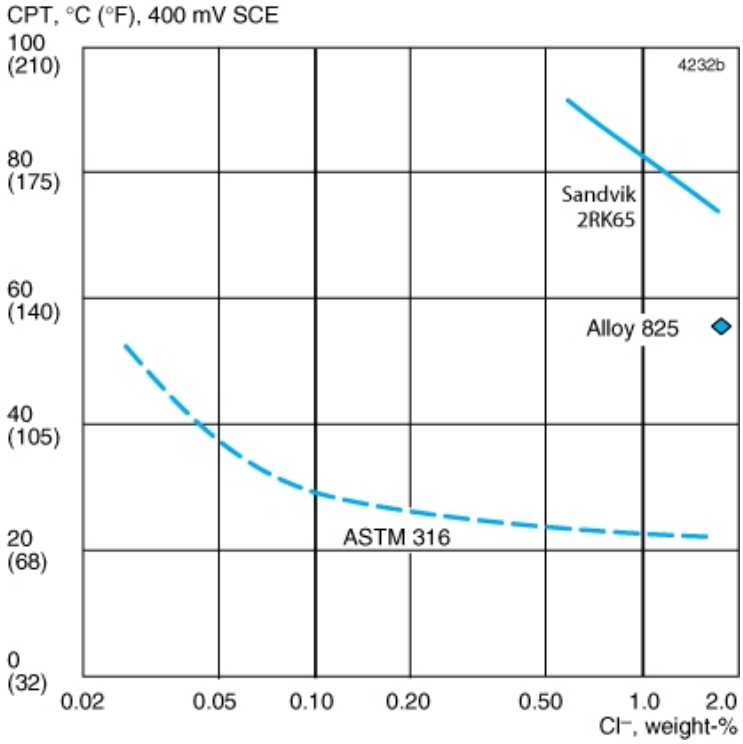



Figure 8. Mean values of critical pitting temperature (CPT) at 400 mV SCE and different Cl<sup>-</sup> concentrations (NaCl solutions), pH ~ 6 (1.8%Cl<sup>-</sup> corresponds to the chloride content of seawater).

As can be seen in Figure 8, the mean critical pitting temperature (CPT) for Sandvik 2RK65™ is around 75°C (165°F) at a potential of 400 mV SCE in a neutral solution (pH = 6) with the same chloride content as seawater. This value is 50°C (120°F) higher than for ASTM 316 and 20°C (68°F) higher than for Alloy 825 (21Cr42Ni3Mo).

### Stress corrosion cracking (SCC)

Ordinary austenitic steels of the ASTM 304 and ASTM 316 types are susceptible to stress corrosion cracking (SCC) in chloride-bearing solutions at temperatures above about 60°C (140°F). At high temperatures, above about 100°C (212°F), chloride contents as low as in the ppm-range ($10^{-4}$ %) are sufficient to cause stress corrosion cracking in these steels. A nickel content of 25% is sufficient to provide very good resistance under practical conditions.

Laboratory tests in calcium chloride confirm the superiority of Sandvik 2RK65™ in resisting stress corrosion cracking compared to ASTM 304 and ASTM 316. As is shown by figure 9, the threshold stress (the stress necessary to induce fracture within the maximum testing time) is considerably higher for Sandvik 2RK65™ than for ASTM 304 and ASTM 316. Sandvik 2RK65™ is resistant up to at least 0.9 times the tensile strength.

Autoclave tests at different chloride contents and temperatures provide valuable data for material selection. Also this type of testing demonstrates the good SCC-resistance of Sandvik 2RK65™, far better than ASTM 304 and ASTM 316 types of steels, see Figure 10.

It is important to be aware of the fact that the residual stresses around a weld that has not been heat treated often equal the proof strength of the material. These stresses correspond to applied stress/tensile strength ratios of only 0.3–0.5, which is sufficient to exceed the threshold stress and thereby cause stress corrosion cracking in ASTM 304 and ASTM 316.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

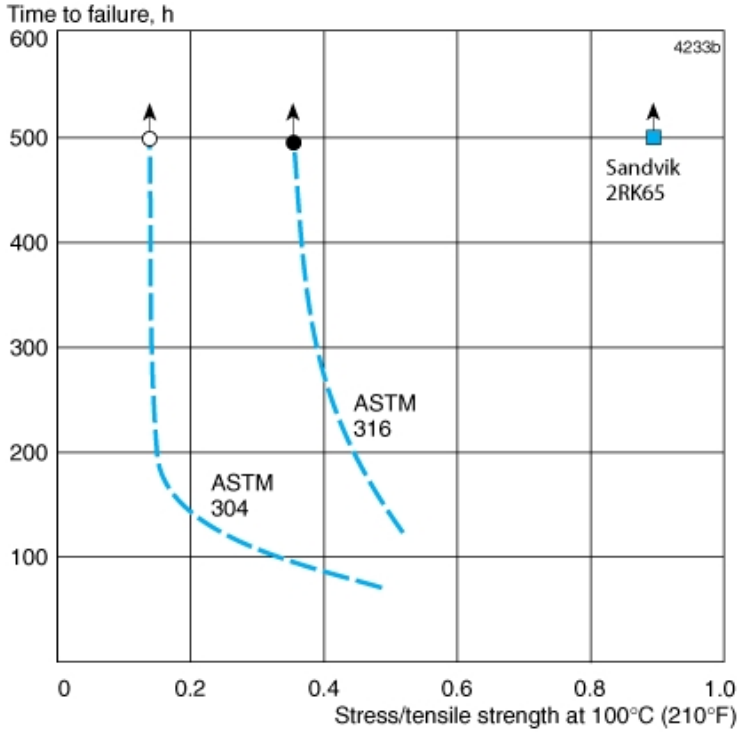



Figure 9. Results of stress corrosion cracking tests on different steel grades in 40% CaCl<sub>2</sub> at 100°C (210°F), pH = 6.5.

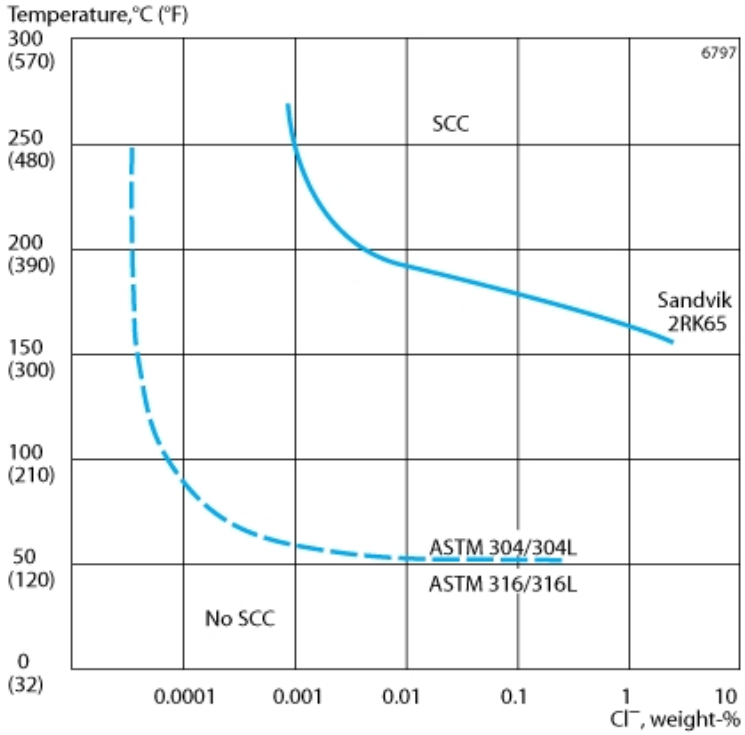



Figure 10. SCC resistance of 2RK65 in comparison to ASTM 304 and AISI 316 types of steels in neutral aerated chloride

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

environments.

### Crevice corrosion

Both laboratory tests and practical experience have shown that Sandvik 2RK65™ is substantially more resistant to crevice corrosion than ASTM 316L. This is illustrated in Table 2. Crevices should nevertheless be avoided as far as possible, especially in chloride-bearing solutions.

Table 2. Results of crevice corrosion tests in aerated stagnant NaCl solution (1.8% Cl-) pH = 6, test period 58 days. The area ratio between creviced and non-creviced surface on the specimen is 1/12.

**Metric units**

| Grade | Initiated crevice corrosion attacks, % | | | Maximum depth, mm | | |
|---|---|---|---|---|---|---|
| | 50°C | 60°C | 70°C | 50°C | 60°C | 70°C |
| Sandvik 2RK65 | - | 0 | 0 | - | 0 | 0 |
| ASTM 316L | 38 | 21 | - | 0.20 | 0.16 | - |

**Imperial units**

| Grade | Initiated crevice corrosion attacks, % | | | Maximum depth, in. | | |
|---|---|---|---|---|---|---|
| | 120°F | 140°F | 160°F | 120 °F | 140 °F | 160 °F |
| Sandvik 2RK65 | - | 0 | 0 | - | 0 | 0 |
| ASTM 316L | 38 | 21 | - | 0.008 | 0.006 | - |

## BENDING

The good ductility of Sandvik 2RK65™ permits bending in the cold state to the smallest bending radii attainable with modern methods and machines. Annealing is not necessary after cold bending. If, however, the tubes have been heavily cold-worked and are to be used under conditions where stress corrosion cracking (SCC) is liable to occur, solution annealing is recommended (see under 'Heat treatment').

For pressure vessel applications in Germany, heat treatment may be required after cold deformation in accordance with VdTÜV-Wb 421. Heat treatment should be carried out by solution annealing.

## FORMS OF SUPPLY

Seamless tube and pipe are supplied in dimension up to 230 mm (9.1 in.) outside diameter in the solution annealed and white-pickled condition or in the bright-annealed condition.

Tubes can be bent according to customer drawings and, on request, annealed after bending.

### Fittings

90 deg. bends are manufactured as standard in Sandvik 2RK65™ according to ANSI B16.9 and, where applicable, ASTM A403. Flanges are made as standard to ANSI B16.5 in the form of slip-on flanges (class 150) and weld neck flanges (class 300), and to relevant sections of ASTM A182. Fittings can be manufactured to other standards by agreement. Other types of fittings such as reducers, tees and couplings can also be supplied on request.

### Other products forms

- Welded tube and pipe
- Strip, annealed or cold-rolled to different degrees of hardness
- Wire, drawn or ground

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

- Bar steel
- Plate and sheet
- Forged tube-sheets

## HEAT TREATMENT

### Solution annealing

The tubes are delivered in heat treated condition. If additional heat treatment is needed after further processing the following is recommended.

1080–1150°C (1975–2100°F), 5–30 minutes, rapid quenching in air or water.

## MECHANICAL PROPERTIES

The following figures apply to material in the solution annealed condition. Tube and pipe with thickness above 20 mm (0.79 in.) may have slightly lower values.

**Metric units, at 20°C**

| Proof strength | | Tensile strength | Elong. | | Hardness |
|---|---|---|---|---|---|
| $R_{p0.2}$[a)] | $R_{p1.0}$[a)] | $R_m$ | A[b)] | $A_{2"}$ | Vickers |
| MPa | MPa | MPa | % | % | |
| | | | | | approx. |
| ≥230 | ≥250 | 520-720 | ≥35[c)] | ≥35 | 160 |

1 MPa = 1 N/mm²

**Imperial units, at 68°F**

| Proof strength | | Tensile strength | Elong. | | Hardness |
|---|---|---|---|---|---|
| $R_{p0.2}$[a)] | $R_{p1.0}$[a)] | $R_m$ | A[b)] | $A_{2"}$ | Vickers |
| ksi | ksi | ksi | % | | |
| | | | | | approx. |
| ≥33 | ≥36 | 75-104 | ≥35[c)] | ≥35 | 160 |

a) $R_{p0.2}$ and $R_{p1.0}$ correspond to 0.2% offset and 1.0% offset yield strength, respectively.
b) Based on $L_0 = 5.65 \sqrt{S_0}$ where $L_0$ is the original gauge length and $S_0$ the original cross-section area.
c) NFA 49–217 with min 40% can be fulfilled.

### Impact strength

Due to its austenitic microstructure, Sandvik 2RK65™ has very good impact strength both at room temperature and at cryogenic temperatures.

Tests have demonstrated that the steel fulfils the requirements (60 J (44 ft-lb) at -196°C (-320°F)) according to the European standards EN 13445-2 (UFPV-2) and EN 10216-5.

### At high temperatures

The steel should not be exposed to temperatures above about 550°C (1020°F) for prolonged periods, since this leads to precipitation of intermetallic phases, which can have an adverse effect on both the mechanical properties and the corrosion resistance of the steel.

**Metric units**

| Temperature | Proof strength | |
|---|---|---|
| | $R_{p0.2}$ | $R_{p1.0}$ |

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

| °C | MPa | MPa |
|---|---|---|
| | min. | min. |
| 100 | 176 | 205 |
| 200 | 155 | 185 |
| 300 | 136 | 165 |
| 400 | 125 | 155 |

**Imperial units**

| Temperature | Proof strength | |
|---|---|---|
| | $R_{p0.2}$ | $R_{p1.0}$ |
| °F | ksi | ksi |
| | min. | min. |
| 200 | 26.1 | 30.3 |
| 400 | 22.4 | 26.7 |
| 600 | 19.5 | 23.7 |
| 700 | 18.6 | 22.9 |

## PHYSICAL PROPERTIES

**Density:** 8.0 g/cm³, 0.29 lb/in³

**Thermal conductivity**

| Temperature, °C | W/(m °C) | Temperature, °F | Btu/(ft h °F) |
|---|---|---|---|
| 20 | 12 | 68 | 7 |
| 100 | 14 | 200 | 8 |
| 200 | 16 | 400 | 9 |
| 300 | 18 | 600 | 10.5 |
| 400 | 20 | 800 | 11.5 |
| 500 | 22 | 1000 | 13 |
| 600 | 23 | 1200 | 14 |
| 700 | 25 | 1300 | 14.5 |

**Specific heat capacity**

| Temperature, °C | J/(kg °C) | Temperature, °F | Btu/(lb °F) |
|---|---|---|---|
| 20 | 460 | 68 | 0.11 |
| 100 | 485 | 200 | 0.12 |
| 200 | 515 | 400 | 0.12 |
| 300 | 545 | 600 | 0.13 |
| 400 | 570 | 800 | 0.14 |
| 500 | 590 | 1000 | 0.14 |
| 600 | 605 | 1200 | 0.15 |
| 700 | 615 | 1300 | 0.15 |

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)



Tel: +45 63 12 83 00 | Email: ps@hymatik.com | www.hymatik.com | Hvidkaervej 27a, DK-5250 Odense SV, Denmark

### Thermal expansion[1)]

| Temperature, °C | Per °C | Temperature, °F | Per °F |
|---|---|---|---|
| 30-100 | 15.5 | 86-200 | 8.5 |
| 30-200 | 16 | 86-400 | 9 |
| 30-300 | 16.5 | 86-600 | 9 |
| 30-400 | 17 | 86-800 | 9.5 |
| 30-500 | 17 | 86-1000 | 9.5 |
| 30-600 | 17.5 | 86-1200 | 9.5 |
| 30-700 | 17.5 | 86-1300 | 10 |

1) Mean values in temperature ranges ($x10^{-6}$)

### Resistivity

| Temperature, °C | μΩm | Temperature, °F | μΩin. |
|---|---|---|---|
| 20 | 0.94 | 68 | 37.0 |
| 100 | 0.99 | 200 | 38.8 |
| 200 | 1.07 | 400 | 42.2 |
| 300 | 1.13 | 600 | 44.6 |
| 400 | 1.15 | 800 | 45.5 |
| 500 | 1.17 | 1000 | 45.8 |
| 600 | 1.15 | 1200 | 45.9 |
| 700 | 1.18 | 1300 | 46.5 |

### Modulus of elasticity[1)]

| Temperature, °C | MPa | Temperature, °F | ksi |
|---|---|---|---|
| 20 | 195 | 68 | 28.5 |
| 100 | 190 | 200 | 27.5 |
| 200 | 182 | 400 | 26.5 |
| 300 | 174 | 600 | 25 |
| 400 | 166 | 800 | 24 |
| 500 | 158 | 1000 | 22.5 |

1) ($x10^{3}$)

## WELDING

Other forms of supply

Remove – Welding consumables

Welding

The weldability of Sandvik 2RK65™ is good. Welding must be carried out without preheating, and normally there is no need for any subsequent heat treatment. Suitable methods of fusion welding are manual metal-arc welding (MMA/SMAW) and gas-shielded arc welding, with the TIG/GTAW method as first choice.

In common with all fully austenitic stainless steels, Sandvik 2RK65™ has low thermal conductivity and high thermal expansion. Welding plans should therefore be carefully selected in advance, so that distortions of the

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

welded joint are minimized. If residual stresses are a concern, solution annealing can be performed after welding.

For Sandvik 2RK65™, heat-input of <1.0 kJ/mm and interpass temperature of <100°C (210°F) are recommended. A string bead welding technique should be used.

### Recommended filler metals

TIG/GTAW or MIG/GMAW welding

ISO 14343 S 20 25 5 Cu L/ AWS A5.9 ER385 (e.g. Exaton 20.25.5.LCu)

MMA/SMAW welding

ISO 3581 E 20 25 5 Cu N L R/ AWS A5.4 E385-16 (e.g. Exaton 20.25.5.LCuR)

ISO 14343 S 20 25 5 Cu L wire or strip electrodes are recommended for overlay welding of tube sheets and high-pressure vessels in cases where corrosion resistance, equal to that of Sandvik 2RK65™, is required.

Disclaimer: Recommendations are for guidance only, and the suitability of a material for a specific application can be confirmed only when we know the actual service conditions. Continuous development may necessitate changes in technical data without notice. This datasheet is only valid for Sandvik materials.

Datasheet updated 1/17/2020 4:07:49 PM (supersedes all previous editions)

materials.sandvik/contact-us
MATERIALS.SANDVIK